

STEVENS ROOFING SYSTEMS ADHERED STEVENS EP-FLEECE

TABLE OF CONTENTS

	PAGE
Part 1	General
1.01	Description EP Fleece 03.06.1
1.02	Quality assurance EP Fleece 03.06.1
1.03	Submittals EP Fleece 03.06.1
1.04	Delivery and storage EP Fleece 03.06.2
1.05	Precautions EP Fleece 03.06.2
1.06	Warranty EP Fleece 03.06.2
Part 2	Products
2.01	General EP Fleece 03.06.2
2.02	Membrane EP Fleece 03.06.3
2.03	Related materials EP Fleece 03.06.3
Part 3	Execution
3.01	Substrate preparation EP Fleece 03.06.5
3.02	Applications procedures EP Fleece 03.06.6
3.03	Fastening requirements EP Fleece 03.06.10
Tables and Charts	
Table 1	-Physical Properties EP Fleece 03.06.3
Table 2	-ASCE Chart EP Fleece 03.06.11
Table 3	-EP Fleece Physical Properties EP Fleece 03.06.11
Appendix A -Fastener Selection Guide	
Appendix FA-B-Approved Insulation list	

Please note: Other Stevens EP Specs are available on the Stevens Technical Manual CD-Rom and on-line at www.stevensroofing.com

CSI Division 7 Guide Specifications

STEVENS EP™-FLEECE ADHERED ROOFING SYSTEM

PART 1 - GENERAL

1.01 Description

- A.** Furnish and install an adhered Stevens EP-Fleece Roofing System in accordance with drawings and specifications approved by Stevens Roofing Systems (Stevens).

Special Conditions

1. This specification is intended for building roofs that have deck structures meeting guidelines herein and have no abnormally severe or unknown environmental exposures, e.g. coastal winds or certain chemicals except as specifically authorized herein.
2. Applications that involve severe exposures, (ASCE Ground Roughness Category D) require review by Stevens Roofing Systems Technical Review Dept. before any specification is valid (*Reference Table 2, ASCE Exposure Classification Chart*).

WARNING: Buildings operating with interior positive pressure at the deck require review by Stevens Technical Review Dept. before any specification is valid.

- B. Related work:** Metal work other than Stevens Edge Metal Systems is not covered by Stevens for warranty. Metal work must be secured in a manner approved by Stevens and/or in accordance with SMACNA guidelines to prevent damage from buckling or wind exposure. All metal work that is part of the waterproofing envelope must be sealed, structurally sound, and appropriately anchored to prevent leakage.

1.02 Quality assurance

- A.** Apply roofing system using a roofing applicator authorized by Stevens.
- B.** Stevens EP-Fleece membrane is classified by Underwriters Laboratories as a Class A sheathing material for use in construction of Class A roofing assemblies. See UL's *Roofing Materials and Systems Directory* for specific assemblies. Adhered Stevens EP-Fleece system

testing has met all requirements for Factory Mutual Global (FMG) Class 1A Fire and wind resistance as outlined in FMG Standard 4470 (Reference current edition of FMG Approval Guide).

- C. Inspection:** Upon completion of the installation, an inspection shall be performed by a representative of Stevens to ascertain that the roofing membrane system has been installed according to Stevens-approved specifications and details. Upon approval of the project, a warranty shall be written.
- D. Changes:** Should there be deviations or changes from this specification without written approval of Stevens, the project is not authorized for installation and is not eligible for warranty coverage.
- E.** Stevens EP membrane is manufactured in an ISO-9001:2000 facility.

1.03 Submittals

- A.** Minimum job file submittal information for consideration for labor and material warranty coverage shall be an accurately completed Request for Warranty form (www.stevensRFW.com) and the information discussed in paragraph B, following.
- B.** Samples and data sheets of all materials not supplied or approved by Stevens shall be submitted to Stevens for written approval prior to the start of installation. Authorized applicators must submit a roof drawing indicating which details will be employed in the project. These drawings shall be approved by Stevens prior to the start of work. These must include: outline and size of the roof, location and type of penetrations, perimeter and penetration flashing detail references, and a copy of any non-SR details to be used. Details which do not conform to Stevens standard SR Detail Drawings, must be shown as to their anticipated construction.
- C.** For a Limited Membrane Material-Only Warranty, the Request for Membrane Warranty form is the only submittal required.

1.04 Delivery and storage

- A. All materials provided by Stevens shall be delivered with appropriate packaging, labels indicating warnings, storage conditions, lot numbers, and usage instructions.
- B. Materials shall be stored in original undamaged packaging and storage conditions shall be maintained in accordance with manufacturers' requirements.

1.05 Precautions

- A. Adhesives, solvents, and caulks as indicated are extremely flammable and/or toxic. Follow precautions indicated on container or packaging labels.
- B. Surfaces to be bonded shall be dry, clean and free of debris. Suitable surfaces are usually considered to be smooth: concrete, wood, and insulation boards fastened to the specific manufacturer's recommendations for receiving adhered roofing membranes and accepted by Stevens for adhered applications of Stevens EP-Fleece membrane.
- C. All fasteners are recommended to be installed with a depth-sensing screw gun to prevent overdriving or underdriving. The ASAP and PIF adapter tools are recommended for the installation of Stevens ASAP and Stevens PIF Fasteners.
- D. Block off or shut down positive pressure building ventilation systems during application to prevent sheet from billowing during application.
- E. Consideration should be given in the project design to potential safety problems that can precipitate from the smooth surface characteristic of the Stevens EP-Fleece sheet. The membrane surface becomes slippery when wet. If access to roof is required, walkway surfaces are recommended. In northern climates, sliding snow could create a hazard below and adjacent to the perimeter if a retarding system is not installed on roofs with slopes greater than 2-in. per foot.
- F. Job specification and retrofit preparation should always include provision to ensure positive drainage in all areas. Good roofing practice does not permit uncontrolled, uncollected drainage over the edge of a roof.
- G. All rooftop mechanical units are to have their condensation lines piped to drains or off the roof.
- H. Grease shall not be allowed to accumulate on

the roof. If rooftop grease units are not to receive a continual maintenance program they are to have an approved grease containment system specified.

- I. At the discretion of Stevens, excessive patching as a result of damage to the Stevens EP-Fleece membrane or caused by faulty installation may require total recover in those areas.
- J. For buildings with canopies or large wall openings, e.g. hangar doors and truck entrances or docks, which are subject to positive pressurization from wind or from air handling systems, consult Stevens for suitability of application and possible design enhancement requirements.
- K. Stevens EP-Fleece membrane is to be installed on roofs with a maximum slope of two inches (2-in.) in twelve inches (12-in.).
- L. Block off or shut down rooftop fresh-air intakes and secure ventilation systems that recycle air through open cavities between ceilings and roof deck. Operation of HVAC equipment shall be coordinated with building owner to ensure fresh air intake vents do not operate in the vicinity of the adhesive application to prevent vapors from entering the building.

1.06 Warranty

- A. A Stevens representative shall inspect the installation for compliance with applicable Stevens specifications upon completion of the roofing system.
- B. Upon acceptance through inspection, Stevens Standard or Total System Warranty will be issued for a five (5), ten (10) or fifteen (15) year period covering wind damage at up to 60 mph for systems where Stevens EP is adhered directly to deck, systems with mechanically attached insulation and for systems with insulation secured using a Stevens-supplied insulation adhesive. Warranty wind coverage for systems using other insulation adhesives will be limited to gale force wind coverage.
- C. Reference General Warranty Section of the Stevens Technical Manual CD-Rom for more information.

PART 2 - PRODUCTS

2.01 GENERAL

- A. All material shall be furnished, specified or approved in writing by Stevens. Samples of all materials used on the project that are not supplied by Stevens shall be furnished to Stevens for

Table 1 - Physical Properties - Stevens EP

Physical Property	Test Method	Typical Values 45 mil* (1.14 mm)	Typical Values 60 mil* (1.52 mm)	Typical Values 80 mil* (2.03 mm)
Breaking Strength	ASTMD-751	275 lbf.(1.2 kN)	320 lbf.(1.4 kN)	390 lbf. (1.7 kN)
Tear Strength	ASTMD-751 Procedure B, 8"x8" sample)	135 lbf.(.60 kN)	110 lbf.(.49 kN)	104 lbf. (.46 kN)
Dimensional Stability (% change max.)	ASTM D-6878 (white: 6 hrs. @ 158°F/70°C)	±0.3	±0.3	±0.2
Hydrostatic Resistance	ASTM D-751 (Method A)	400 psi (2.8 MPa)	425 psi (2.9 MPa)	510 psi (3.52 MPa)
Ozone Resistance**	ASTMD-1149 (70 hrs.@100°F/37.8°C)	Pass	Pass	Pass
Weather Resistance	Xenon Arc, ASTM D-6878 G-155; 5040 kJ/m ² 0.35w/m ² @ 340nm	No cracks, loss of breaking strength, or tear strength	No cracks, loss of breaking strength, or tear strength	No cracks, loss of breaking strength, or tear strength
	EMMAQUA (Concentrated Natural Sunlight) (ASTM G-90) 167 MJ/m ² total UV radiant exposure	Pass	Pass	Pass
Puncture Resistance	FTM 101B (Method 2031)	330 lbf. (1.5 kN)	400 lbf. (1.8 kN)	500 lbf. (2.2 kN)
Water Vapor Transmission	ASTM E-96 (Procedure B Condition BW @ 72°F/22.2°C)	0.035 Perms	0.035 Perms	0.035 Perms
Elongation (%) Ultimate**	ASTMD-412 (Die C)	700%	700%	700%
Brittleness	ASTMD-2137 @ -49°F/-45°C	Pass	Pass	Pass
Water Absorption (max. % weight change)**	ASTMD-6878 D-471, (158°F/70°C for 7 days) Testing only one side section	±3	±3	±3
Heat Aging	ASTMD-6878 D-573 (28 days @ 240°F/115°C)	Break: 275 lbf. (1.2 kN)	Break: 320 lbf. (1.4 kN)	Break: 350 lbf. (1.56 kN)
Solar Reflectance (initial)	ASTM E-903	>70%	>70%	>70%
Thermal Emittance	ASTME-408	>0.93	>0.93	>0.93

*Thickness (nominal) per ASTM D-751 test method.
**Test performed on non-reinforced Stevens EP membrane.

written approval prior to the start of work.

2.02 Membrane

- A.** Membrane for roof cover shall be .045-in or .060-in. nominal thickness overall, scrim reinforced, Ethylene Propylene-based sheet 76.5-in. wide by appropriate length conforming to the minimum physical properties in Table 1, *Physical Properties Chart*, laminated to a nonwoven polyester fleece-backing, conforming to the minimum physical properties in Table 3, *Physical Properties Chart*. Stevens EP-Fleece membrane has a 3.5-in. (nominal) selvage edge of non-fleeced area of membrane the length of the sheeting to allow for hot-air welding seam overlaps. Stevens EP-Fleece membrane is available in White and Light Gray. Stevens EP membranes meet the ASTM 6878-03 specification for TPO-based roofing material. Package to bear the UL label.

2.03 Related materials

- A. Insulation/underlayment/recover board:** Stevens supplies a wide range of insulations, underlayments and coverboards to satisfy a broad spectrum of design

conditions. Only Stevens brand insulation products will be eligible for Total System Warranty coverage: products other than Stevens will incur a premium warranty fee. (*Reference Appendix FA-B, Stevens Approved insulation List and Fastening Rates for Mechanically Attached Systems*).

- 1. Stevens ISO 2000:** Closed-cell HCFC FREE “Green” polyisocyanurate foam core manufactured using (HCFC) (ACUltra Hydrocarbon) blowing agent and integrally laminated to heavy non-asphaltic fiber-reinforced felt facers; compressive strength - (20 psi) (25 psi). Available in flat stock and tapered panels. (*Reference Stevens Product Specification Data Sheets for additional information*).
- 2. Stevens ISO 3000:** Closed-cell HCFC FREE “Green” polyisocyanurate foam core manufactured using (HCFC) (ACUltra Hydrocarbon) blowing agent and integrally laminated to heavy coated-glass facers; compressive strength - (20 psi) (25 psi). (*Reference Stevens Product Specification Data Sheets for additional information*).
- 3. Stevens ISO Recover Board:** Closed-cell HCFC FREE “Green” polyisocyanurate

foam core manufactured using (HCFC) (ACUltrahydrocarbond) blowing agent and integrally laminated to heavy coated-glass facers; compressive strength - (20 psi) (*Reference Stevens Product Specification Data Sheets for additional information*).

4. Stevens Extruded Polystyrene (XPS):

Extruded polystyrene closed-cell foam panel with continuous skin on face and back surface that meets ASTM C-578, Standard Specification for Rigid Cellular Polystyrene Thermal Insulation. (*Reference Stevens Product Specification Data Sheets for additional information*).

5. Stevens Expanded Polystyrene (EPS):

ASTM C578-04a expanded polystyrene thermal rigid board insulation with a minimum density of 1.25 lbs./cu.ft.(ft3). (*Reference Stevens Product Specification Data Sheets for additional information*).

6. DensDeck® Roof Boards: (*Reference Stevens Product Specification Data Sheets for additional information*).

- a. G-P Gypsum Corporation 1/4-in. DensDeck Roof Board, 1/2-in. DensDeck Roof Board and 5/8-in. Type X Roof Board. Nonstructural, glass mat faced gypsum panel with water-resistant core available in 4-ft.x8-ft. sizes and 4-ft.x4-ft. sizes
- b. G-P Gypsum Corporation 1/4-in. DensDeck Prime Roof Board, 1/2-in. DensDeck Prime Roof Board and 5/8-in. DensDeck Prime Roof Board (Type X). Glass mat faced gypsum with non-asphaltic, highly filled proprietary heat-cured coating on one side available in 4-ft.x8-ft. and 4-ft.x4-ft. sizes.
- c. G-P Gypsum Corporation 1/4-in. DensDeck DuraGuard, 1/2-in. DensDeck Duraguard and 5/8-in. DensDeck Duraguard. Glass mat faced gypsum panel with blue low-perm, durable, integrated-coating on one side and coated glass mat on the back available in 4-ft.x8-ft. and 4-ft.x4-ft. sizes.

B. Flashing: Flashing shall be .045-in. thick membrane for walls and curbs regardless of roof cover sheet thickness. Unsupported .055-in. thick, Ethylene Propylene-based membrane shall be supplied for field-fabricated vent stacks, pipes, drains and corners. Stevens EP-Clad Metal may be used for gravel stops or drip edges.

C. Adhesive, Primers, Caulks and Sealant:

1. Stevens EP (TPO) Bonding Adhesive:

Stevens EP (TPO) Bonding Adhesive is designed for bonding all Stevens EP membranes to wood, metal, masonry, and approved roof insulation board surfaces. Stevens EP Bonding Adhesive is **not** approved for use with other roofing membrane types or Stevens EP-Fleece membrane.

2. Stevens All-Purpose Sealant: Stevens All-Purpose Sealant is designed to be used as a water cutoff mastic, sealant to top off pitch boxes, as an exterior grade caulk for metal work.

3. Stevens EP Cut-Edge Sealant: Stevens EP Cut-Edge Sealant is a solvent-based caulk developed to seal exposed cut edges of reinforced membrane.

4. Stevens Insulation Adhesives: Stevens offers multiple insulation adhesive options.

- a. Stevens Insulation Adhesive is a VOC-free, one-part, rising, moisture-cure foam that is poured from 1 or 2.5 gallon cans on the substrate.
- b. Stevens-Olybond 500 is a two part, polyurethane low rise foam that is applied in ribbons with appropriate dispensing equipment.
- c. Stevens-Olybond Classic is a two part, polyurethane low rise foam that is spray applied to fully cover the substrate.

Stevens Insulation Adhesives are designed for bonding most insulation and recover boards to a wide range of substrates and other insulation boards. Please consult the appropriate Product Specification Data Sheet for detailed information.

5. Stevens EP Seam Cleaner: Stevens EP Seam Cleaner is a surface cleaner for use with Stevens EP membranes that have become dirty or contaminated prior to heat welding.

D. Perimeter sheets:

- 1. Stevens published fastening rates and perimeter enhancement requirements are not necessarily consistent with the requirements of local building codes, FMG or similar agencies. Consult said agencies for their specific requirements when necessary or contact the Stevens Technical Review Dept.
- 2. Perimeter Sheet specification is defined as

Stevens EP membrane with a minimum width of 38.25 in. and a maximum width of 52.5 in.

- 3. For buildings less than 70-ft. high in wind zones within ASCE Ground Roughness Categories A, B and C (Reference Table 2, ASCE Ground Roughness):** two perimeter sheets shall be installed at all exterior roof perimeters that are not bordered by a parapet wall or an adjoining building a minimum of 24-in. higher than roof level. Perimeter sheet requirement pertains to any adjoining roof level 2-ft. or greater above the main deck level. Reference special condition fastening variations (reference 3.03) for guidelines addressing more severe exposures (ASCE Ground Roughness category D) and buildings greater than 70- ft. high.

E. Mechanical fasteners: Shall be supplied by Stevens.

1. Membrane:

- a.** Refer to *Appendix A, Stevens Fastener Selection Guide* to select appropriate fastener/plate combination and approved fastening rates. Also, Stevens Product Data Sheets can be found on the Stevens Technical Manual CD-Rom.
- b.** For gypsum, cementitious woodfiber decks (“Tectum”) and light-gauge metal panel roofs, fastener pull tests must be submitted to Stevens Technical Review Dept. with the project Request for Warranty form (RFW).

2. Insulation:

- a.** Refer to *Appendix A, Stevens Fastener Selection Guide* and *Appendix FA-B, Stevens Approved Insulation List and Fastening Rates for Fully Adhered Systems*, for approvals and fastening requirements. Also, product data sheets can be found on the Stevens Technical Manual CD-Rom.
- b.** For gypsum, cementitious woodfiber decks (“Tectum”) and light-gauge metal panel roofs, fastener pull tests must be submitted to Stevens Technical Review Dept. with the project Request for Warranty Form (RFW).

F. Termination bar: Stevens Termination Bar fastened 6-in. o.c. is the only authorized product.

G. Stevens Edge Metal Systems: Stevens Edge Metal must be installed per standard SR

details.

H. Roof walkways: When roof traffic is indicated (for example to service rooftop units), a walkway over the membrane shall be made. Stevens EP Walkway Roll heat welded to the membrane is recommended.

I. Prefabricated Stevens EP Pipe Boots: Are provided as an alternative to .055-in. unsupported flashing for vent stacks and pipes 1-in. to 6-in. diameter.

J. Prefabricated Stevens EP Corners: Are provided as an alternative to .055-in. unsupported flashing for use at outside and inside corners.

K. Stevens EP Flashing Tape: 6-in. wide x 70-mils thick, packaged 100-ft. rolls. This product is made with unsupported membrane with a butyl tape backing (with a release paper) and is the preferred method for stripping-in non-Stevens gravel stop and drip edge metal (not for use on Stevens Clad Metal). Flashing Tape eliminates the need for Stevens (TPO) Bonding Adhesive and Stevens All-Purpose Sealant when completing edge flashings. Surfaces must be prepared with Stevens Tape Primer prior to Flashing Tape application.

PART 3 - EXECUTION

3.01 Substrate preparation

A. The applicator shall be responsible for the suitability of the substrate surface to accept Stevens EP-Fleece membrane. In reroofing, test cuts shall be made by the roofing applicator to determine existing condition and deck suitability. All noticeably damp, wet or deteriorated materials must be removed. In all cases, prior to the start of work, the substrate shall be smooth and free of debris, sharp edges, and other surface irregularities that will be detrimental to the installation. Any unevenness or joint gaps greater than 1/4-in. in the membrane substrate can cause inconsistent membrane welds and must be avoided. When such conditions occur, fill with appropriate and properly secured insulation or material approved by Stevens Technical Review Dept.

B. Steel deck, wood plank and light-weight cementitious decks: Shall be covered with an approved insulation mechanically fastened or adhered to deck with Stevens approved products (*Reference Appendix FA-B, Stevens Approved Insulation List & Fastening Rates for fully adhered systems*).

C. Concrete and plywood: Stevens EP-Fleece membrane may be adhered directly to concrete and plywood decks. Plywood must be exterior grade with an A or B finish side up, with no joints gapped greater than 1/4-in. Consideration should be given to installing slip plates at all gapped or uneven joints where membrane seams will cross to minimize welding inconsistency. Thickness, structural grade, fastening and fireproofing should meet the requirements and recommendations of applicable building codes and the APA and are the responsibility of the owner and the installer. Concrete must be dry, fully cured and prepared smooth with dust removed. The membrane shall have a fastened expansion joint detail (as per standard SR Detail Drawings) where deck joints exceed 1/4-in. or when crossing a building expansion joint.

D. Reroofing over existing roof: The specifier and/or applicator shall determine the condition of the existing roof. Significantly deteriorated decking must be repaired or replaced, as appropriate. Wet materials (containing free moisture that would evaporate if exposed to atmosphere) must be found and replaced. Existing surface shall be dry, reasonably smooth and even, blisters cut, and loose aggregate removed prior to installation of approved insulation board.

E. Vapor retarder: Is not required for protection of Stevens Roofing System Membrane. As a guideline, the National Roofing Contractors Association states, "...vapor retarders should be considered for use when both of two conditions are anticipated: (1) the outside mean, average January temperature is below 40°F (4.4°C), and (2) the expected winter, interior relative humidity is 45 percent or greater."

NOTE: In all high humidity situations consult Stevens Technical Review Dept. and the insulation manufacturer for specific application requirements.

F. Nailers: Pressure preservative treated, wooden nailers shall be installed at gravel stops or drip edges.

1. Reroofing: Use #2 or better wood treated for rot resistance. Creosote and asphaltic preservatives are not acceptable.

2. New roofing: A pressure preservative treated wood nailer is recommended. Effective perimeter attachment must be achieved per details and/or as specified by architect/designer.

3. All construction: Nailer should be anchored with a suitable fastener for the application having a minimum withdrawal resistance of 100-lbs. staggered 6-in. o.c. within 8-ft. of an outside corner, and 12-in. o.c. along other perimeter areas.

4. All construction: Nailer thickness shall be chosen to match the top surface of adjacent construction $\pm 1/4$ -in. This permissible variation shall not contribute to ponding.

5. Nailers around skylights, curbs, expansion joints, etc., are not required. Use of Stevens fasteners and plates anchored to deck 12-in. o.c. (except tall building applications see [section 3.03.C](#)) through membrane and insulation is acceptable.

G. Existing flashings: Must be removed and completely cleaned off wherever new Stevens Roofing System terminations and water stops are to be installed. Existing flashings may be left in place up to Stevens termination areas when in good structural condition and solidly attached to substrate.

H. New construction or reroof with complete tearoffs of flashings: The applicator shall be responsible for the suitability of the substrate surface to accept the Stevens EP-Fleece membrane. The substrate shall be smooth and free of sharp edges and other surface irregularities that will be detrimental to the 100% adhesion of the flashing membrane.

3.02 Application procedures

NOTE: For insulation application and suitability refer to [Appendix FA-B, Stevens Approved Insulation List & Fastening Rates for fully adhered systems](#).

A. Insulation or protection board:

1. Minimum thickness: Shall be approved in writing by Stevens. Since the insulation requirement for thermal value will vary for each project, the thickness of the insulation must be calculated for the desired results.

2. Compatibility: Certain insulation such as polystyrene is not compatible with coal tar pitch. Contact manufacturer for recommendations. Certain polystyrene insulation boards are not suitable for use directly under Stevens EP colored membrane and require an overlayment ([Reference Appendix FA-B, Stevens Approved Insulation List and Fastening Rates for Fully Adhered Systems](#)).

3. Manufacturer's instructions: In regard to attachment compatibility and spanning of metal flutes, the manufacturer's specifications shall determine the suitability for an application, subject to acceptance by Stevens.

4. Precautions: Be careful when handling insulation boards, as well as in their mechanical attachment, so as to not damage or rupture the facer and surface. All damaged areas must be cut out and replaced with structurally sound insulation, properly secured in place.

5. Attachment: Insulation boards must be secured sufficiently to conform to the substrate surface geometry.

a. Mechanical attachment: All boards must be attached with FMG and Stevens-approved insulation plates and appropriate fasteners. For Total System Warranty applications insulation plates and fasteners must be supplied by Stevens (*Reference Appendix A, Stevens Fastener Selection Guide and Appendix FA-B, Stevens Approved Insulation List & Fastening Rates for Fully Adhered Systems*).

b. Adhered insulation adhesive: As an alternative to mechanical attachment, Stevens permits adhering insulation with a Stevens-supplied insulation adhesive. Stevens Insulation Adhesives are the only products eligible for Stevens warranty coverage. Insulation boards must be secured sufficiently to conform to the substrate surface geometry.

c. Adhered insulation with Asphalt: As an alternative to mechanical attachment, Stevens permits adhering insulation with hot steep asphalt (ASTM D-312 Type III or IV). The specific application must be approved in writing from the insulation board manufacturer and be approved by Stevens Technical Review Dept. All temperature requirements and application procedures must be followed. Insulation boards must be secured sufficiently to conform to the substrate surface geometry.

6. Approved insulation shall be laid with its end joints staggered. Boards shall be butted as closely as possible with no gaps over 1/4-in. and attached as specified in 3.02.A.5.

7. Tapered insulation: Most tapered insula-

tion systems taper down to a minimum 1/2-in. thickness only. Therefore, a tapered edge strip of high density fiber board must be used to provide a smooth transition to the flat areas.

B. Membrane installation procedures:

1. For roofs with interior drainage, start with first sheet centered on drain valley. Fold sheet so that the bottom side half of the full length of sheet is exposed.
2. Apply a 100% continuous coat of Stevens EP-Fleece Water-based Bonding Adhesive to the area of substrate exposed by folding membrane back. Work evenly across the area to ensure membrane will be rolled into wet adhesive. Reapply adhesive to any areas that have dried or skinned over.

NOTE: Adhesive must be spread out by roller as necessary to achieve 100% coverage on the substrate. Adhesive should never be broomed or mopped. Adhesive must not be cut or extended. Outside ambient air temperature must be a minimum 50°F and rising. Adhesive should not be stored below 40°F.

3. Carefully unroll the folded section of Stevens EP-Fleece membrane and lower it onto the glued substrate surface while adhesive is wet, avoiding any wrinkles or air pockets. Immediately broom the adhered area applying pressure to promote full contact.

NOTE: Summer ambient conditions may dictate adhering smaller areas of membrane at a time to prevent over drying of adhesive.

4. Repeat the procedure for the other half of the sheet.
5. For roofs with edge drainage, start at the low edge with the first sheet and follow the procedure described in the preceding paragraph (*Reference paragraph 3.02.B.7 following*).

NOTE: Adhesive coverage should be 100 square feet per gallon for coating substrate only. This will consume about 5 to 6 gallons of adhesive per standard (76.5-in. x 100 ft.) roll of membrane if applied without excessive waste. Cold weather, inconsistent spreading, and rough or porous substrate (i.e. Dens-Deck® or concrete) will consume more adhesive. Membrane must have 100% adhesion to the approved substrate.

6. Layout the second sheet with a 2-in. overlap on the edge of the first sheet. Perform lap

splice per Section 3.02.C. After splice has cooled, completely expose the bottom side of the second sheet by folding back along the splice. Apply adhesive evenly to substrate surface only, carefully turn membrane back onto glued substrate surface while adhesive is still wet, avoiding any wrinkles or air pockets. Apply only enough adhesive to an area of the substrate to ensure membrane will be rolled into wet adhesive. Broom surface applying pressure to promote full contact. Repeat procedure for each sheet proceeding across roof.

CAUTION: Starting membrane application at high points may be necessary if the substrate type prevents effective tie offs or if it is not possible to complete roof area to the high point (ridge) by the end of the day.

WARNING: If adhesive has been contaminated by blowing dust, moisture, walking in it, etc. it should be allowed to completely dry (no longer tacky) and new adhesive applied.

7. At perimeters that are to receive a gravel stop or metal edging, the Stevens EP-Fleece membrane must be brought over the outside edge and terminated 12-in. o.c. unless otherwise stated in the appropriate detail.
8. Membrane must be mechanically attached 12-in. o.c. at all perimeters and at any penetration that has a dimension of 24-in. or greater with Stevens Fasteners and Plates.

C. Lap splice: Membrane shall be overlapped and hot-air welded without any contaminants (adhesive, dirt, debris, etc.) prevalent in the seam. For areas of Stevens EP-Fleece membrane that do not have a selvage edge, weld a coverstrip of standard 6-in. wide reinforced Stevens EP (non fleece) membrane (Reference Section 2.03.A) over butted joint.

1. **Hot-air welding:** An automatic hot-air welder and hand-held welder which are functionally in top condition are a necessity for Stevens applications. Small work and repairs can be done efficiently with the hand-held welders; however, hand-held welders are not a recommended means of field seaming.
2. **The entire lap edge must be probed** with approved seam probing tool (Sears cotter pin extractor) after it has cooled completely to verify seam consistency. Probing before the seam area has cooled will damage the membrane. In addition there

should be destructive tests performed daily on a 3-in. wide area of seam weld to verify sufficient peel strength. A properly welded seam will have membrane delamination from scrim prior to weld failure. Destructive tests on welds should be done for the first seam of the day, first seam after the robot welder has been allowed to cool down, and after any extreme changes in weather conditions. Cut edges shall be caulked by applying Stevens EP Cut-Edge Sealant from a squeeze bottle.

3. T-Seams.

- a. **Definition:** The point where two perpendicular lap seams intersect is called a “T-seam” and if T-seams are not properly welded, a seam void may result.
- b. For .045-in. and .060-in. membrane, T-seams should be properly creased in at the step-off area, using a hand roller. For T-seam locations that have not been welded properly, a patch is required. Patches shall be a minimum of 4-in. in diameter and can be either .045-in. reinforced Stevens EP membrane or .055-in. unsupported membrane.

4. Stevens EP membrane, as with any material after exposure, will require cleaning prior to seaming.

The approved method for removing contaminants from the Stevens EP membrane prior to welding is as follows:

- a. Remove any visible dirt and debris with a clean rag and water. For heavily contaminated surfaces, scrubbing with a detergent cleaner (i.e. Fantastik® or 409®) followed by a water rinse may be necessary.
- b. With a clean scrub pad saturated with Stevens EP Seam Cleaner, aggressively agitate the seaming area. With a clean white rag, follow with a final one swipe pass over the seaming area, without redepositing any contaminants.
- c. Allow Stevens EP Seam Cleaner to completely flash off (i.e. membrane should be completely dry).
- d. Follow the standard hot-air welding procedures with an approximated 20% reduction in speed.
- e. Final weld strength may not be achieved for several days.

D. Perimeter fastening: Wood nailers are

required for perimeter gravel stops or drip edges. Membrane may be fastened at other transitions, using Stevens Fasteners and Plates.

- 1. Wooden nailers:** Reference Section 3.01.F.
- 2. Base of parapet or curb:** Membrane shall be mechanically fastened 12-in. o.c. through insulation (and existing roof in reroofing) into deck. Fastening shall occur at parapet wall, curbs, skylights, expansion joints, and any other roof penetrations that exceed 24-in. in any dimension (*Reference specific standard SR Detail Drawings*).

CAUTION: Deck membrane must be adhered up to and/or past these fastening points regardless of whether or not adhesive is shown in any detail that may be referenced.

E. Flashing: Perimeters, curbs, vents, expansion joints, drains, and other details shall be flashed as shown in standard SR Detail Drawings. Under no condition shall flashings cover weep holes or any form of through-wall drainage.

1. Apply Stevens EP (TPO) Bonding Adhesive to both underside of Stevens EP membrane and surface to which it is to be bonded, at a rate of approximately one gallon per 60 square feet of surface coverage (when applied to two surfaces).

NOTE: Stevens EP (TPO) Bonding Adhesive shall not be applied to that portion of the flashing that overlaps onto itself. Hot-air welding shall be used throughout the system where Stevens EP membrane overlaps itself.

2. Stevens EP (TPO) Bonding Adhesive shall be allowed to dry until tacky and until it does not string or stick to a dry finger. Roll the flashing into the dry adhesive. Care must be taken to assure that the flashing does not bridge where there is any elevation or directional change. Completely roll the flashing membrane against the substrate using a hand roller, J-roller or similar device applying firm pressure to the entire surface area.
3. All flashing shall be terminated as shown in standard SR Detail Drawings.
4. Stevens Metal flashing at perimeter shall be made and installed as per standard SR Detail Drawings.
5. Pipe flashings shall be installed in accordance with standard SR Detail Drawings. Remove existing flashings and sleeves. Do not flash to lead.

6. Expansion joints shall be installed in accordance with standard SR Detail Drawings.
7. Roof drains shall be installed in accordance with standard SR Details. When Stevens EP-Fleece membrane is used to complete the drain detail, the fleece backing must be removed at drain bowl juncture prior to caulking. In reroofing, old drains must be cleaned or replaced as needed for clamping detail. All bolts must be properly secured to supply 100% continuous compression of the clamping ring. Remove old leads and packings. Field seams shall not be run through drains. Drain sleeves are not covered under warranty. However, premanufactured sleeve insert with clamping ring and backflow seal are acceptable.

F. Metal work: Metal work other than Stevens Edge Metal Systems is not covered by Stevens Warranty.

1. Metal work shall be installed in a manner that prevents damage from buckling or wind.
2. All metal work must be sealed and waterproofed in an acceptable manner.

G. Overnight seal/temporary water stop: Shall be made by a sealant method approved by Stevens to protect the insulation from inclement weather at the end of a day's work. The membrane is extended beyond the insulation and set into the approved overnight seal material. Roofing applicator shall coordinate installation to ensure the system is made watertight at the end of each work day.

H. Roof walkways: When regular roof traffic is indicated (for example, to service rooftop units), Stevens EP Walkway Roll is recommended to be installed over the membrane.

Installation:

For dirty and/or weathered membrane, start with #1 below. For clean fresh membrane, start with #4 below.

1. Stevens EP-Fleece membrane must be clean and dry. Remove any visible dirt and debris with a clean rag and water. For heavily contaminated surface, scrubbing with a detergent cleaner (i.e. Fanstik® or 409®) followed by a water rinse may be necessary.
2. With a clean scrub pad saturated with Stevens EP Seam Cleaner, aggressively agitate the seaming area of the roof membrane surface. With a clean white rag,

follow with a final one swipe pass without redepositing any contaminants.

3. Allow Steven EP Seam Cleaner to completely flash off (i.e. membrane should be completely dry).
4. Position Walkway Roll and cut to desired length. In circumstances where drainage around the walkway is a concern, shorter walkway lengths spaced with a 2-in. gap may be desired.

Whenever possible, walkway shall not cover seams. When installed adjacent to a seam, the walkway should be kept a minimum of 2-in. from the edge of the seam on the bottom sheet of the completed lap and a minimum of 6-in. from the edge of the seam when located on the top sheet of a completed lap.

When covering seams is unavoidable, the lap seam should be completed per Stevens Specifications and thoroughly probed with any deficiencies repaired prior to walkway installation.

5. Weld perimeter of walkway to the membrane following standard welding procedures. Periodic breaks in the weld of 1 to 2-in. are required on the low slope edge of the pad to prevent the accumulation of water under the pad.

3.03 Fastening Requirements

The following fastening requirements apply to membrane with widths of 76.5-in. or less. Fastening patterns are for minimum 3/4-in. plank/plywood, 22 gauge steel or heavier and minimum 2500 psi compressive strength structural concrete decks on buildings located within ASCE Ground Roughness Categories A, B and C (*Reference ASCE Exposure Classification Chart*). For approved fastener and plate combinations refer to *Appendix A, Stevens Fastener Selection Guide*.

A. Buildings up to 70-ft. high

1. No additional requirement to those listed above for perimeters and penetrations.

B. Buildings over 70-ft. up to 150-ft. high

1. One full-width sheet (76.5-in.) shall be laid out in a picture frame pattern around the perimeter and fully adhered per specifications (unless perimeter is bordered by a 3-ft. or higher parapet wall).
2. The outer side of the perimeter sheet shall be fastened per the approved perimeter detail. The field side seam shall be fastened at 9-in. o.c.

3. For mechanically attached insulation the fasteners per board should be increased from the field fastening approval rate by 50% in the perimeter area* and 75% in the corner area* (corner area is defined as the intersection of the two perimeter area bands).

* Perimeter area shall be defined as the smaller of:
0.1 times the building lesser plan dimension.
0.4 times the eaves height.

C. Buildings over 150-ft. high

1. Requires prior approval by Stevens and special specifications contact Stevens Technical Review Dept.

D. Special Conditions: Restriction for coastal and abnormal wind uplift applications.

Typical considerations:

1. ASCE Exposure D.
2. Buildings over 350-ft.
3. Buildings with positive pressure.
4. Canopy construction.
5. Hangar facilities or buildings with wall openings greater than 10% of a side wall area.

General design recommendation:

Any one of the above factors is a valid reason to consider increased perimeter and field fastening. Stevens may require enhanced system design in the absence of significant compensating factors. Stevens should be consulted before committing to a design and/or cost.

Table 2 - ASCE Exposure Classification

ASCE Exposure Classifications Defined

ASCE (American Society of Civil Engineers) has defined the roughness of the terrain into four “ground roughness” categories, or “exposures”.

Exposure A	This classification applies to large city centers with at least 50 percent of the buildings having a height in excess of 70 feet (21.3 m). Use of this exposure category shall be limited to those areas for which representative terrain prevails in the upwind direction for a distance of at least one-half mile (0.8 km) or 10 times the height of the building or structure, whichever is greater. Possible channeling effects or increased velocity pressures due to the building or structure being located in the wake of adjacent buildings shall be taken into account.
Exposure B	Urban and suburban areas, wooded areas, or other terrain with numerous closely spaced obstructions having the size of a single-family dwelling or larger. Use of this exposure category shall be limited to those areas for which representative terrain prevails in the upwind direction for a distance of at least 1,500 feet (460 m) or 10 times the height of the building or structure, whichever is greater.
Exposure C	Open terrain with scattered obstructions having heights generally less than 30 feet (9.1 m). This category includes flat, open country and grasslands.
Exposure D	Flat, unobstructed areas exposed to wind flowing over open water for a distance of at least one mile (1.61 km). This exposure shall apply only to those buildings and other structures exposed to the wind coming from over the water. Exposure D extends inland from the shoreline a distance of 1,500 feet (460 m) or 10 times the height of the building or structure, whichever is greater.

Table 3 - Physical Properties - Stevens EP-Fleece











Physical Property	Test Method	Typical Values 45 mil* (1.14 mm)	Typical Values 60 mil* (1.52 mm)
Thickness	ASTMD-751	45 mil membrane plus fleece	60 mil membrane plus fleece
Breaking Strength	ASTMD-751	340 lbf. (1.5 kN)	400 lbf. (1.8 kN)
Tear Strength	ASTMD-751 Procedure B, 8"x8" sample)	135 lbf. (.60 kN)	120 lbf. (.53 kN)
Dimensional Stability (% change max.)	ASTM D-6878 (white: 6 hrs. @ 158°F/70°C)	±0.3	±0.2
Hydrostatic Resistance	ASTMD-751 (Method A)	500 psi (3.5 MPa)	540 psi (3.7 MPa)
Ozone Resistance**	ASTMD-1149 (70 hrs. @ 100°F/37.8°C)	Pass	Pass
Weather Resistance	Xenon Arc, ASTM D-6878 G-155; 5040 kJ/m ² 0.35w/m ² @ 340nm	No cracks, loss of breaking strength, or tear strength	No cracks, loss of breaking strength, or tear strength
	EMMAQUA (Concentrated Natural Sunlight) (ASTM G-90) 167 359 MJ/m ² total UV radiant exposure	Pass	Pass
Puncture Resistance	FTM 101B (Method 2031)	450 lbf. (2.0 kN)	500 lbf. (2.2 kN)
Water Vapor Transmission	ASTM E-96 (Procedure B Condition BW @ 72°F/22.2°C)	0.035 Perms	0.035 Perms
Elongation (%) Ultimate**	ASTMD-412 (Die C)	700%	700%
Brittleness	ASTMD-2137 @ -49°F/-45°C	Pass	Pass
Water Absorption (max. % weight change)**	ASTMD-6878 D-471, (158°F/70°C for 7 days) Testing only one side section	±3	±3
Heat Aging	ASTMD-6878 D-573 (28 days @ 240°F/115°C)	Break: 340 lbf. (1.5 kN)	Break: 400 lbf. (1.8 kN)
Solar Reflectance (initial)	ASTM E-903	>70%	>70%
Thermal Emittance	ASTME-408	>0.93	>0.93




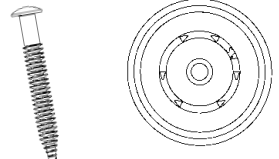



*Thickness (nominal) per ASTM D-751 test method.

**Test performed on non-reinforced Stevens EP membrane.

STEVENS ROOFING SYSTEMS FASTENER SELECTION GUIDE

APPENDIX A

				
<p>PRODUCT DESCRIPTION: Stevens #14 All-Purpose Fastener</p>	<p>PRODUCT DESCRIPTION: Stevens #12 Insulation Fastener</p>	<p>PRODUCT DESCRIPTION: Stevens Maxfast Fasteners</p>	<p>PRODUCT DESCRIPTION: Stevens Purlin Fasteners</p>	<p>PRODUCT DESCRIPTION: Stevens DeckGrip Fastener</p>
<p>All-purpose fastener for membrane and insulation attachment. Use with 2-inch (50-mm) BMSP or Hex Insulation Plate.</p>	<p>General purpose fastener for insulation attachment. Use with Hex Insulation Plate.</p>	<p>A large diameter head fastener for membrane attachment. Use with Maxfast Plate only.</p>	<p>A roofing fastener for membrane attachment to structural steel purlins in standing seam metal roof retrofit applications.</p>	<p>#15 fastener for membrane and insulation attachment. Used for Stevens EP and EV membrane</p>
<p>SIZE AVAILABLE: 1¼, 2, 3, 4, 5-8-inch (30, 50, 75, 100, 125 - 200 - mm) in 1-inch (25-mm) increments and 10 and 12-inch (250 and 300-mm).</p>	<p>SIZE AVAILABLE: 1⁵/₈, 2¼, 2⁷/₈, 3¼, 3¾, 4½, (41, 57, 73, 85, 95, 114-mm) 5 - 8-inch (125 - 200-mm) in 1-inch (25-mm) increments</p>	<p>SIZE AVAILABLE: 2 - 8-inch(50 - 200-mm) in 1-inch (25-mm) increments</p>	<p>SIZE AVAILABLE: Overall Length: 3¾, 4¾, 5¾, 7 and 8-inch (95, 120, 146 , 178 and 200-mm) Note: Usable length is ¾-inch (19-mm) less than overall length to allow the screw to quickly drill thru the purlin before the threads engage.</p>	<p>SIZE AVAILABLE: 1¼, 2, -8, 10, 12, 14 and 16-inch (30, 50 - 200, 250, 300, 355 and 406-mm)</p>
<p>DECK TYPE: Structural concrete (pre-drilling required), wood and 18 to 26 (1.3 - .55-mm) gauge steel.</p>	<p>DECK TYPE: Wood and 18 to 26 (1.3 - .55-mm) gauge steel</p>	<p>DECK TYPE: FM approved minimum 22 gauge steel* [*Test drill to check for installability on 18 and 20 (1.3 - 2.5-mm) gauge steel decks prior to committing to a project].</p>	<p>DECK TYPE: 18-12 (1.3 - 2.5-mm) gauge steel</p>	<p>DECK TYPE: Structural concrete (pre-drilling required), wood and 18 to 26 (1.3 - .55-mm) gauge steel.</p>
<p>PACKAGING: 1¼ - 6-inch (30 - 150-mm): 1000/bucket 7, 8, 10, 12-inch (175, 200, 250, 300-mm): 500/bucket</p>	<p>PACKAGING 1⁵/₈ - 6-inch (41 - 150-mm): 1000/bucket 7 and 8-inch (175 and 200-mm): 500/bucket</p>	<p>PACKAGING: 2 and 3-inch (50 and 75-mm): 1000/bucket 4 - 6-inch (100 - 150-mm): 500/bucket 7 and 8-inch (175 and 200-mm): 250/bucket</p>	<p>PACKAGING: 500/box</p>	<p>PACKAGING: 1¼ (30-mm) 2, -5 -inch (50 -125-mm): 1000/box 6, 7, 8 , 10, 12, 14-inch (150, 175, 200 250, 300, 355-mm): 500/box and 16-inch (406-mm)250/box</p>
				
<p>PRODUCT DESCRIPTION: Stevens 2-in. (50 mm) Barbed Metal Seam Plates (for membrane attachment)</p>	<p>PRODUCT DESCRIPTION: Stevens Hex Insulation</p>	<p>PRODUCT DESCRIPTION: Stevens Maxfast Plate</p>	<p>PRODUCT DESCRIPTION: Stevens 2" Purlin Plate</p>	<p>PRODUCT DESCRIPTION: Stevens DeckGrip Plate</p>
<p>2-inch (50-mm) Galvalume® coated steel barbed seam plate for use with Stevens #14-10 fasteners or Stevens CD-10 concrete fasteners.</p> <p>SIZE AVAILABLE: 2-inch (50-mm) round barbed</p> <p>DECK TYPE: NA</p> <p>PACKAGING: 1,000/bucket</p>	<p>2⁷/₈-inch (73-mm) Hex-shaped Galvalume coated steel insulation plate for use with Stevens #12, #14 or Stevens CD-10 concrete fasteners.</p> <p>SIZE AVAILABLE: 2⁷/₈-inch (73-mm) diameter</p> <p>DECK TYPE: NA</p> <p>PACKAGING 1000/box</p>	<p>A 3-inch (76-mm) diameter plate for use only with the Stevens Maxfast Fastener for membrane attachment.</p> <p>SIZE AVAILABLE: 3-inch (76-mm) diameter</p> <p>DECK TYPE: NA</p> <p>PACKAGING: 500/bucket</p>	<p>A 2-inch (50-mm)diameter barbed metal seam plate designed to accommodate the head of the Stevens Purlin fastener. Use of other Stevens Plates may be necessary depending on project requirements.**</p> <p>SIZE AVAILABLE: 2-inches (50-mm)</p> <p>DECK TYPE: NA</p> <p>PACKAGING: 1000/box</p>	<p>Galvalume steel seam plate featuring a unique patented "Eye Hook" design.</p> <p>Stevens DeckGrip Reel-Fast Collated Seam Plates for easy installation. Spaced 6-in.(150 mm) or 12-in. (300 mm) o.c. (see separate datasheet)</p> <p>SIZE AVAILABLE: 2 3/8-inch (60-mm)</p> <p>DECK TYPE: NA</p> <p>PACKAGING: 1000/bucket</p>

			
<p>PRODUCT DESCRIPTION: Stevens PIF (Preassembled insulation plate & fastener)</p> <p>Preassembled #12 (black) fastener with 3-inch (75-mm) (blue) locking plate for insulation attachment.</p> <p>SIZE AVAILABLE: 2¼, 2⅞, 4½, 5 - 8-inch (57, 73, 114, 127 - 200-mm) in 1-inch (25-mm) increments plus 10 and 12-inch (250 and 300 -mm). Other lengths available on special order.</p> <p>DECK TYPE: Wood and 18 to 26 (1.3 -.55 -mm) gauge steel.</p> <p>PACKAGING 2¼ - 8-inch (57 - 200-mm): 250/box 10-inch (250-mm) and longer: 200/box</p>	<p>PRODUCT DESCRIPTION: Stevens ASAP (Preassembled membrane seam plate & fastener)</p> <p>All-purpose #14 fastener pre-assembled with 2-inch (50-mm) (gray) nylon locking plate for membrane attachment.</p> <p>SIZE AVAILABLE: 2 - 8-inch (50 - 200-mm) in 1-inch (25 -mm) increments plus 10, 12, and 14-inch (250, 300, 355-mm) and other lengths available on special order.</p> <p>DECK TYPE: Structural concrete (pre-drilling required), wood and 18 to 26 gauge (1.3 - .55-mm) steel.</p> <p>PACKAGING: 2 and 3-inch (50 and 75-mm): 500/per box; 4-inch (100-mm): 450/box; 5-inch (125-mm) 400/box; 6-inch (150-mm): 350/box; 7 and 8-inch (175 and 200-mm): 300/box; 10 - 12-inch (250 and 300-mm): 200/box; 14-inch (355-mm): 150/box</p>	<p>PRODUCT DESCRIPTION: Stevens Preassembled DeckGrip</p> <p>Preassembled membrane seam plate & fastener</p> <p>SIZE AVAILABLE: 2 - 8, 10, and 12-inch (50 - 200, 250 and 300-mm)</p> <p>DECK TYPE: Structural concrete (pre-drilling required), wood and 18 to 26 gauge (1.3 - .55-mm) steel.</p> <p>PACKAGING: 2 and 3-inch (50 and 75-mm): 500/box 4 - 8-inch (100 - 200-mm) 250/box 10,12-inch (250, 300-mm) 125/box</p>	<p>PRODUCT DESCRIPTION: Stevens SW Fastener and Plate Kits</p> <p>A "Superior Withdrawal" fastener for membrane attachment with 23/8-inch (60-mm) SW Barbed Metal Seam Plate.</p> <p>SIZE AVAILABLE: 2 - 8-inch(50 - 200-mm) in 1-inch (25-mm) increments</p> <p>DECK TYPE: FM Approved minimum 22 (.85-mm) gauge steel* (*Test drill to check for installability on 20 (1.0-mm) gauge steel decks prior to committing to a project).</p> <p>PACKAGING: 2 - 8-inch (50 - 200-mm) 250 fasteners and plates/bucket</p>
			
<p>PRODUCT DESCRIPTION: Stevens CD-10 Concrete Fastener</p> <p>Non-threaded hammer-in (spike type) fastener for membrane and insulation attachment.</p> <p>SIZE AVAILABLE: 2 - 4-inch (50 - 100-mm) in ½-inch (13-mm) increments, 4 - 10-inch (100-250-mm) in 1-inch (25-mm) increments, and 12-inch (300 -mm)</p> <p>DECK TYPE: Structural concrete</p> <p>PACKAGING: 2 - 8-inch (50 - 200-mm): 500/box 9-inch (228-mm) and longer: 250/box</p>	<p>PRODUCT DESCRIPTION: Stevens Masonry Anchor</p> <p>Hammer-in-type fastener for securing termination bar.</p> <p>SIZE AVAILABLE: 1/4-inch (6-mm) diameter x 1¼-inch (30-mm) length</p> <p>FOR USE IN: Concrete and masonry</p> <p>PACKAGING: 1,000/box</p>	<p>PRODUCT DESCRIPTION: Stevens Termination Bar</p> <p>Aluminum bar for use in membrane termination. Refer to specific SR details.</p> <p>SIZE AVAILABLE: 1-inch (25-mm) wide, 10-ft. (3-m) long 6-inch (150-mm) o/c slotted, punched</p> <p>DECK TYPE: N/A</p> <p>PACKAGING: 500-ft. (152-m)/tube 50 pcs,10-ft. (3-m) long</p>	



Appendix FA-B

(page 1 of 2)

STEVENS Approved Insulation List and Fastening Rates (Chart 5) for Adhered Roofing Systems

Introduction

This is a listing of insulation and cover board products acceptable for use with Stevens Adhered Roofing Systems. Each listing shows specific manufacturer and product names, indicates which products are approved for retrofit applications and which are eligible for Stevens "Total System" Warranty coverage. In addition, fastening recommendations for each product type are shown.

Note: It is not within the scope of this chart to provide information relating to building code compliance, or specific Factory Mutual Global or Underwriters Laboratories, Inc. approvals. FMG, UL and/or building code requirements for insulation type, thermal barrier requirements, minimum/maximum insulation thickness and product pre-securement rates may differ from the Stevens requirements shown herein. Refer to the current edition of the FMG Approval Guide, the UL Roofing Materials and Systems Directory and/or the UL Fire Resistance Directory for complete information, or contact the Stevens Technical Review Dept. In addition, consultation with local building department is recommended to ensure compliance with applicable requirements.

General Recommendations

- 1) Refer to the product manufacturer's literature to confirm minimum allowable thickness required to span steel deck flutes, etc.
- 2) Adjacent insulation/cover boards shall be installed as closely as possible with no gaps or offsets greater than 1/4 inch.
- 3) A tapered edging of Stevens approved insulation is required at step transitions greater than 1/4-in. (as is typical for polyisocyanurate panels that taper to 1/2-in. only).
- 4) Approved insulation products shall be installed with the longest dimension of the board perpendicular to the direction of mechanically secured membrane lap seams whenever possible. Insulation end joints shall be staggered.
- 5) Insulation pre-securement fasteners/plates shall be installed at the rates shown herein and located on each board as shown in Stevens detail drawings SR-622A, 622B and 622C.
- 6) For applicable substrates, Stevens permits insulation boards to be adhered using a Stevens-supplied insulation adhesive, hot steep asphalt (ASTM D312, type III and IV) and some commercial insulation adhesive products. The insulation manufacturer, adhesive manufacturer and Stevens Technical Services must specifically approve such applications.
- 7) Consult the Stevens Technical Review Department at (877)788-8324 if the insulation manufacturer's current installation/securement instructions conflict with information published herein.

For Products Not Listed Herein

In the event that you wish to use an insulation product that does not appear on the Stevens Approved Insulation list, please contact the Stevens Technical Review Dept. at (877) 788-8324 for recommendations prior to commencement of the project.

Rev: 050106

STEVENS Approved Insulation List and Fastening Rates (Chart 5) for Adhered Roofing Systems

Insulation Type	Approved Manufacturers	Approved Product Name	Approved for Retrofit Applications	Approved for Stevens "Total System" Warranty	Fastening Rate for <i>Field Areas</i> ¹ (see Note 2 for fastening rates at perimeter and corner areas)		
					Product Thickness of 1.4" and less	Product Thickness of 1.4" to 1.9"	Product Thickness of 2" and Greater
Gypsum Board	Georgia-Pacific Corp.	1/4" Dens-Deck®	(see note 3)	Yes	15 per 4'x 8' bd.	N/A	N/A
		1/4" Dens-Deck Prime®			12 per 4'x 8' bd.		
		1/2" Dens-Deck®	Yes		15 per 4'x 8' bd.		
		1/2" Dens-Deck Prime®			12 per 4'x 8' bd.		
	USG	1/4" Securock®	Yes	Yes	10 per 4'x 8' bd	N/A	N/A
		3/8" Securock®					
		1/2" Securock®					
5/8" securock®							
Oriented Strand Board (OSB)	APA Rated Product	1/2" nominal thickness	Yes (when used as a cover board)	N/A	12 per 4'x 8' bd.; 6 per 4'x4' bd.	N/A	N/A
Polyisocyanurate	STEVENS Roofing Systems	Iso-2000, Iso-2000 Tapered, Iso-3000, Iso-3000 Tapered	Yes	Yes	16 per 4'x 8' bd.; 8 per 4'x4' bd.	11 per 4'x 8' bd.; 6 per 4'x4' bd.	8 per 4'x 8' bd.; 4 per 4'x4' bd.
	Atlas Roofing Corporation	AC Foam II®, AC Foam III®	Yes		16 per 4'x 8' bd.; 8 per 4'x4' bd.	11 per 4'x 8' bd.; 6 per 4'x4' bd.	8 per 4'x 8' bd.; 4 per 4'x4' bd.
	Dow Chemical Company	Hy-Therm AP®	Yes	N/A	16 per 4'x 8' bd.; 8 per 4'x4' bd.	16 per 4'x 8' bd.; 8 per 4'x4' bd.	8 per 4'x 8' bd.; 4 per 4'x4' bd.
		Hy-Therm Composite®					
	Dyplast Products, LLC	dpFOAM II™, dpFOAM III™					
	Firestone Building Products	ISO 95+®, ISO 300					
	Hunter Panels, LLC	H-Shield					
Johns Manville Corp.	ENRGY 3™ (flat & tapered)						
Rmax, Inc.	Multi-Max® FA	Yes					
Wood Fiberboard	Knight-Celotex	Structodek™	N/A	N/A	16 per 4'x 8' bd.; 8 per 4'x4' bd.	N/A	N/A
	IKO	Armourdeck					
	Georgia-Pacific Corp.	High Density Roof Fiberboard					
	Temple Inland	HD-1, HD-6	Yes	Yes	12 per 4'x 8' bd.; 6 per 4'x4' bd.		

Notes:

- The fastening rates shown in this chart are applicable for buildings with a height of 70' and less that are located in an ASCE exposure category "A", "B" or "C" (See "Exposure Classification Table" in Stevens Guide Specifications). For fastening variations for buildings over 70' high, buildings in Exposure Category "D" and buildings with abnormal interior conditions, refer to the Adhered System Guide Specifications or contact the Stevens Technical Services Dept. The fastening rates shown here do not necessarily meet the requirements for Factory Mutual Global (FMG) Windstorm Resistance designs. Refer to the FMG "Approval Guide" or contact the Stevens Technical Services.
- Stevens recommends that the fastening rates shown for the Field areas of the roof be increased by 50% at perimeter areas and 75% at corner areas. The extent of perimeter/corner enhancement is based on the smaller value of either 40% of building elevation or 10% of the least horizontal dimension and can not be less than 4% of the least horizontal dimension, or 3-ft. Contact the Stevens Technical Services Dept. at (877)788-8324 with questions.
- This product is not approved as a recovery layer directly over gravel-surfaced B.U.R. roof systems. It is approved for use over existing single-ply and smooth or mineral surfaced roof systems.
- Other insulations / cover boards may be used beneath the products referenced here. Refer to the listing in the Mechanically Attached System Guide Specifications.